



## Design and Characterization of Liposomal Methotrexate and Its Effect on BT-474 Breast Cancer Cell Line

Niloufar Tavakoli Dastjerd<sup>1</sup>, Nematollah Gheibi<sup>2</sup>, Hossein Ahmadpour Yazdi<sup>1</sup>, Hanifeh Shariatifar<sup>3</sup>, Alireza Farasat<sup>1,2\*</sup>

Received: 1 Jan 2021

Published: 29 Nov 2021

### Abstract

**Background:** Breast cancer is the most common type of cancer among women worldwide. Traditional treatments, including chemotherapy, surgery, mastectomy, and radiotherapy, are commonly used. Because of the limitation of the aforementioned methods, novel treatment strategies are needed. Methotrexate is a chemotherapeutic drug, which is commonly used to treat breast cancer. Because of the side effects of the free drug, the liposomal form of the drug is suggested.

**Methods:** Liposomal methotrexate was prepared and the encapsulation efficiency was measured. Moreover, the particle size and the zeta potential were measured. The liposome morphology was confirmed using transmission electron microscopy. The MTT assay was done to examine the cytotoxicity of free and encapsulated methotrexate on BT-474 cell line. The Annexin-V/PI dual staining assay was performed to assess the apoptosis in BT-474 breast cancer cells via the flow cytometry method.

**Results:** The transmission electron microscopy results confirmed the integrated and spherical structure of the nanoparticles. The results of drug release showed that in acidic pH (5.4), more than 90% of the drug was released after 24 hours, which was higher than 2 other pHs. Furthermore, the IC50 value of liposomal methotrexate was determined as 2.15 and 0.82 mg/mL for 24 and 48 hours. The flow cytometry results confirmed that liposomal methotrexate had a greater cytotoxic effect on cancer cells compared with free methotrexate.

**Conclusion:** Because of the advantages of liposomal based nanocarriers, in this study, liposomal methotrexate could be suggested as an appropriate candidate to treat breast cancer.

**Keywords:** Liposome, Methotrexate, BT-474, Breast Cancer, Nanocarriers

**Conflicts of Interest:** None declared

**Funding:** This study was supported by a research grant from Qazvin University of Medical Sciences.

\*This work has been published under CC BY-NC-SA 1.0 license.

Copyright© Iran University of Medical Sciences

**Cite this article as:** Tavakoli Dastjerd N, Gheibi N, Ahmadpour Yazdi H, Shariatifar H, Farasat A. Design and Characterization of Liposomal Methotrexate and Its Effect on BT-474 Breast Cancer Cell Line. *Med J Islam Repub Iran*. 2021 (29 Nov);35:158. <https://doi.org/10.47176/mjiri.35.158>

### Introduction

Breast cancer is the most prevalent type of cancer among women worldwide (1). The effective treatment is remained as a great clinical challenge, although currently

several treatment options are available (2, 3). Breast cancer is classified into 3 main subtypes based on the presence or absence of molecular markers for estrogen or pro-

**Corresponding author:** Dr Alireza Farasat, [a.farasat@qums.ac.ir](mailto:a.farasat@qums.ac.ir)

<sup>1</sup> Medical Biotechnology Department, Faculty of Paramedical Sciences, Qazvin University of Medical Sciences, Qazvin, Iran

<sup>2</sup> Cellular and Molecular Research Center, Research Institute for Prevention of Non-communicable Diseases, Qazvin University of Medical Sciences, Qazvin, Iran

<sup>3</sup> Health Products Safety Research Center, Qazvin University of Medical Sciences, Qazvin, Iran

#### ↑What is “already known” in this topic:

Cancer is one of the leading causes of mortality worldwide. Among women, breast cancer is the most common one. Most of these treatments have severe adverse effects. Chemotherapy has a narrow therapeutic window and requires high dosage treatment in patients with advanced stage cancers who need further innovative treatment strategies.

#### →What this article adds:

Methotrexate (MTX) is an effective drug that might impair malignant growth without irreversible damage to normal tissues. In the current study, we aimed to prepare the liposomal MTX and compare the effects of this drug in free (MTX) and encapsulated forms (MTX-Lip) on BT-474 breast cancer cell line.

gesterone receptors and human epidermal growth factor 2 (ERBB2; previously HER2): positive hormonal receptor/negative ERBB2 (70% of patients), positive ERBB2 (15%-20%), and triple negative breast cancer, which are the tumors that have none of the 3 standard molecular markers (15%) (4, 5).

Treatment usually includes breast conserving surgery (Tumor removal and a margin of surrounding tissue, sometimes called lumpectomy) or mastectomy (complete breast tissue removal), which depends on the characteristics of the tumor and the patient's priority. Furthermore, treatment includes radiotherapy, chemotherapy, hormonal therapy, targeted therapy, and recently immunotherapy (6). Chemotherapy is a process in which, cancerous cells are killed by means of specific drugs (7). The main defects of chemotherapeutic methods at the moment are the non-specific distribution of chemotherapeutic drugs, which causes the drug to affect both normal and tumor cells (8), and their low solubility in aqueous environment, leading to incomplete treatment and serious side effects for the patients (9). Furthermore, cancerous cells are often resistant to these compounds. Multiple drug resistance is related to a wide range of pathological modifications at various cellular and intracellular levels (10). This process includes the reduction of drug transmission, increased efflux, availability of alternative targets, apoptosis prevention (11, 12), lipid membrane alteration, metabolic conversion of drugs, and changes in the main points of the cell cycle and microtubule associated proteins and  $\beta$ -tubulin mutation (13). For these reasons, the therapeutic outlook for these drugs is low (11). MTX is an antimetabolite (folate antagonist), which is used extensively in cancer chemotherapy (14). MTX is a dicarboxylic acid (15), which is competitively bound to the dihydrofolate reductase (DHFR) enzyme, which inhibits the enzyme, depletes tetrahydrofolate cellular storage, and finally leads to thymidylate synthesis cessation (16-18). The DHFR is an essential enzyme that converts dihydrofolate to tetrahydrofolate (19). The cell that does not have enough thymidine cannot synthesize DNA; therefore, it inhibits cell proliferation and growth, which causes the cell arrest in the G1/S phase (16, 17).

MTX is used for the treatment of various solid tumors (eg, osteosarcoma, breast and lung cancer) and also for autoimmune and inflammatory diseases, such as rheumatoid arthritis, Crohn's disease, and psoriasis (16, 20). MTX has been reported to cause apoptosis in various cell lines, but its low accumulation at the tumor site limits its effects on the cells (16). Moreover, MTX causes several side effects such as hepatotoxicity, ulcerative colitis, nephrotoxicity, gastrointestinal disorders, bone marrow toxicity, and pneumonitis, which limit its therapeutic applications (15, 16).

Because of chemotherapeutic methods limitations and the side effects of these drugs, new treatment strategies are required. Nanocarriers are one of the promising new treatment strategies (21). Drug-containing nanocarriers accumulate in target tissues or organs because of various factors, such as barrier's penetration, tissue damage, and environmental pH (22).

Liposomes are one type of nanocarriers that have been widely used for targeted drug delivery. These are vesicles composed of one or more concentric phospholipid bilayers separated by aqueous compartments (23). When used as a carrier, hydrophobic molecules are located in bilayer membrane, and hydrophilic molecules are located in the aqueous center of the liposome (24).

In the current study, we aimed to prepare the liposomal MTX and compare the effects of this drug in free (MTX) and encapsulated forms (MTX-Lip) on BT-474 breast cancer cell line. Furthermore, the drug release was measured in physiological conditions (pH: 7.4), tumor tissue (pH: 6.4), and endosomal compartments (pH: 5.4), respectively.

## Methods

MTX (25 mg) was obtained from Sigma (Aldrich). Phospholipon 90 G and cholesterol were obtained from Avanti Polar Lipids (Alabaster). The BT-474 cell line was obtained from the Leibniz institute of Germany. The RPMI-1640 medium, fetal bovine serum (FBS), penicillin, streptomycin, insulin, glutamine (50x), methanol solution, chloroform solution phosphate buffer saline (PBS), MTT [3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide] solution, dimethyl sulphoxide, and annexin V-FITC apoptosis detection kit were obtained from Sigma (Aldrich).

## Cell Culture

The BT-474 was utilized as HER2-positive cell line. To culture the cells, the RPMI-1640 medium was supplemented with 20% FBS. Then, the streptomycin (100  $\mu$ g/mL), penicillin (100  $\mu$ g/mL), and insulin (10  $\mu$ g/mL) were applied and the cells were incubated at 37°C in a humidified incubator containing 5% CO<sub>2</sub>.

## Preparation of Nanoparticles and Encapsulation of MTX

Prewighed lipids (phospholipon 90G) and cholesterol (70%: 30%) were dissolved in methanol and chloroform (1:1 v/v) solution. The resulting solution was desiccated to shape a thin film layer in a round-bottom flask on a rotary evaporator under low pressure at 33°C until total removal of solvents (25). After adding 1 mL MTX (10 mg/mL) at room temperature, the rehydrated lipid film was extruded (21 $\times$  at 33 °C) through 2 stacked 200 nm polycarbonate membranes (Nucleopore) (Liposofast R) to form unilamellar vesicles. The liposomes were incubated at ambient temperature to cool down and then stored at 4°C. A zeta-sizer apparatus was used to analyze the diameter of produced liposomes.

## Encapsulation Efficiency Determination

**Separation of encapsulated & free drugs:** For this process, the Amicon Ultra-3 (molecular weight cutoff of 3 kDa) was applied. The filter was centrifuged at 5000 g for 15 minutes at 15 °C (26). In this step, the free and encapsulated drugs that were separated from each other were collected in 2 different tubes and stored at 4°C.

**Encapsulation efficiency:** The free MTX absorption

values were read by the UV/Vis spectrophotometer at a wavelength of 300 nm (27). The efficiency of encapsulation was calculated by the following equation (28):

EE stands for encapsulation efficiency:

$$EE\% = (\text{Total MTX} - \text{free MTX} / \text{Total MTX}) \times 100\%.$$

### Liposome Characterization

**Particle Size and Zeta Potential:** The mean size and the zeta potential of liposomal MTX were measured using a dynamic light-scattering detector (Zeta-sizer ZS). A minimum of 3 different batches were assessed to render a mean value and standard deviation for the particle diameter and zeta potential.

**Liposome Morphology:** Liposome formation was confirmed by transmission electron microscopy (TEM, AB-FETEM Leo 9112). Samples were fixed by applying a drop of the mixture to a carbon-coated copper grid and leaving it for 2 minutes to allow some of the particles to attach onto the carbon substrate. The excess dispersion was removed using a piece of filter paper and then, a drop of 1% phosphotungstic acid solution was applied for 1 minute and left to be air-dried. The samples were observed by TEM (29).

**Drug Release Evaluation:** The drug release process of liposomal MTX was tested immediately after the drug was loaded into the liposomes. One mL of drug-loaded liposome solution was suspended inside a dialysis bag (10 kDa) immersed in 20 mL PBS solution at 3 pH levels: 7.4, 6.4, and 5.4. Dialysis bag was continuously stirred in release medium at 300 rpm in a shaker incubator at 37°C. Samples of the released liposomes were taken at 1 to 7 and 24 hours after dialysis started. The free drug concentration was measured using UV/Vis spectrophotometer at 300 nm. The experiments were repeated triplicate and the results were reported.

**Cell Cytotoxicity:** The MTT assay (30) was applied to examine the cytotoxicity of free and encapsulated MTX on BT-474 cell lines. The cells were treated with an increasing concentration (0-5 mg/mL) of each compound for 24 and 48 hours in a 5% CO<sub>2</sub> incubator at 37°C (repeated triplicate). It should be noted that untreated cells were considered as controls. Following incubation, 20 µL MTT solution (5 mg/mL) was added in each well. The result was incubated at 37°C for 24 and 48 hours, and finally the medium was removed, and formazan salt crystals were dissolved by adding 200 µ of dimethyl sulfoxide to each well. Plates were evaluated using an ELISA plate reader (Labsystems multiskan RS-232C, Finland) at 570 and 630 nm.

**Flow Cytometry:** The flow cytometry method was done to confirm the results of MTT assay. The method showed the number of alive, apoptotic, or necrotic cells. The Annexin-V/PI dual staining assay was performed to assess the apoptosis in BT-474 breast cancer cells induced by treatment with free and liposomal MTX (MTX-lip) using fluorescein isothiocyanate (FITC), Annexin V Apoptosis kit and PI (BioLegend). In this process, cells were cultured ( $5 \times 10^5$  cells) in 25 cm<sup>2</sup> cell culture flasks for 48 hours before treatment with free and liposomal MTX. The cells were then treated with IC<sub>50</sub> value of the free and

MTX-lip for 24 and 48 hours. The cells were collected and washed twice with cold PBS, and resuspended in binding buffer ( $1 \times 10^6$  cells/mL). In this step, 1 mL of the cells was transferred into a tube, and then 10 µL of FITC conjugated Annexin V (Annexin V-FITC) and 10 µL of propidium iodide (PI) were added and incubated for 15 minutes at room temperature in dark. The stained cells were diluted by the binding buffer and immediately analyzed using the flow cytometer (Becton Dickinson FACSCanto II (BD FACSCanto II, BD Biosciences)). Data from 10,000 cells were collected in each data file. Four populations of the cells are clearly distinguished, including unlabeled (viable) cells, cells that have bound Annexin V-FITC only (early apoptotic), cells that have been stained with PI (necrotic), and the cells that have bound Annexin V-FITC, and been labelled with PI, which demonstrate the late apoptotic/necrotic cells. All samples were assayed in triplicate and each test was performed 3 times.

## Results

### Preparation and Characterization of Liposomal MTX

The unilamellar vesicles containing MTX were prepared by the thin layer evaporation method. The liposomal MTX nanoparticles were characterized by dynamic light scattering (DLS) and TEM. The TEM observations (Fig. 1) confirmed that these nanoparticles have an integrated, spherical structure. The DLS measurements showed a mean hydrodynamic particle size (Table 1), polydispersity index (PDI), and also zeta potential of empty liposomes (Lip), and liposomal MTX (Table 1).

The results of DLS showed that the addition of MTX to liposomes does not have a significant effect on the size of the nanoparticles. Moreover, the PDI of (MTX/Lip) nanoparticles are desirable and their surface charge was negative. Furthermore, the (MTX/Lip) nanoparticles exhibit an MTX-loading capacity of ~98%.

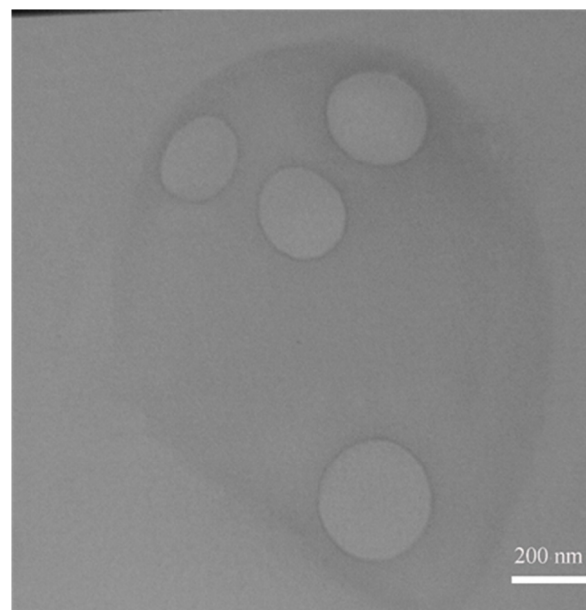


Fig. 1. TEM image of (MTX/Lip) nanoparticles

**Table 1.** Mean hydrodynamic particle size, polydispersity index (PDI) and zeta potential of liposomes (Lip) and liposomal MTX (MTX/Lip)

Formulation	Mean hydrodynamic particle size (nm)	Polydispersity index (PDI)	Zeta potential (mv)
Lip	191.9 ± 2.3	0.140 ± 0.1	-3.18 ± 0.5
MTX/Lip	195 ± 2.2	0.163 ± 0.1	-3.26 ± 0.2


All data are expressed as the mean ± SD (n= 3).

### In Vitro Drug Release


As depicted in Figure 2, the release of the drug (MTX) from liposomes, increased in all 3 pH levels over the time. Furthermore, the MTX release rate was promoted by a decrease in environmental pH. Thus, at pH = 5.4, more than 90% of the drug was released after 24 hours (Fig. 2). These results confirmed that the higher amount of drug could be released at the tumor site, which has the lower pH and it also should be noted that the lowest amount of drug is released at the physiological pH (7.4), which was confirmed by other studies (6, 25).

### In Vitro Cytotoxicity

The cytotoxicity of free and encapsulated MTX were evaluated on BT-474 breast cancer cell line using MTT assay. Different concentrations (0.3 to 5 mg/mL) of free and encapsulated MTX were applied to these cells for 24 and 48 hours (Fig. 3). The cells in the culture medium that were not affected by the drug were considered as controls. Based on Figure 3, the IC<sub>50</sub> value of free drug (MTX) was calculated as 4.85 and 3.62 mg/mL for 24 and 48 hours, respectively. Also, the IC<sub>50</sub> value of the encapsulated drug (MTX/Lip) was determined as 2.15 and 0.82 mg/mL for

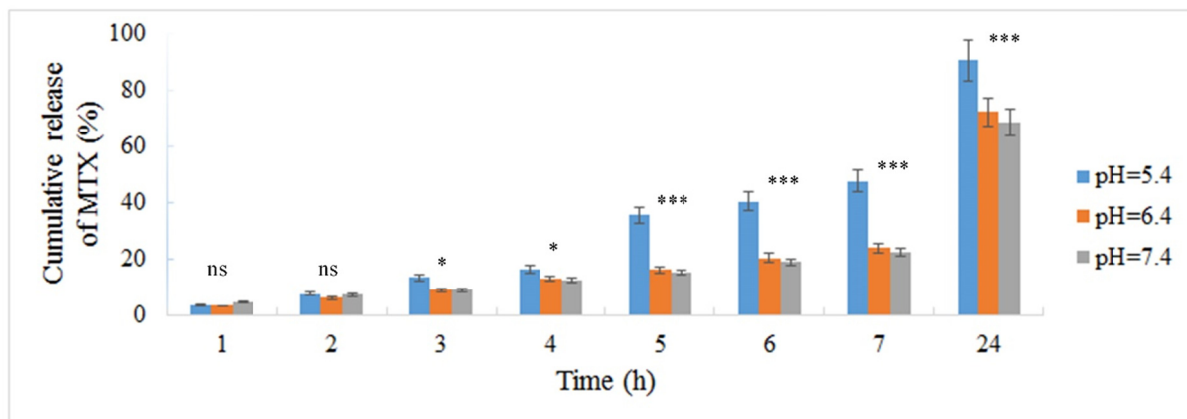

**Fig. 2.** In vitro release profiles of MTX from MTX/Lip in PBS buffer (pH 7.4, 6.4 and 5.4) at 37°C. (Blue, Orange and Grey colors represent pH: 5.4, pH: 6.4 and pH: 7.4). Results of the MTX release were mean ± SD (n=3). \*\*\*p < 0.001 and ns: not significant, it is a comparison between pH: 5.4 and two other pHs (pH: 6.4 and pH: 7.4).

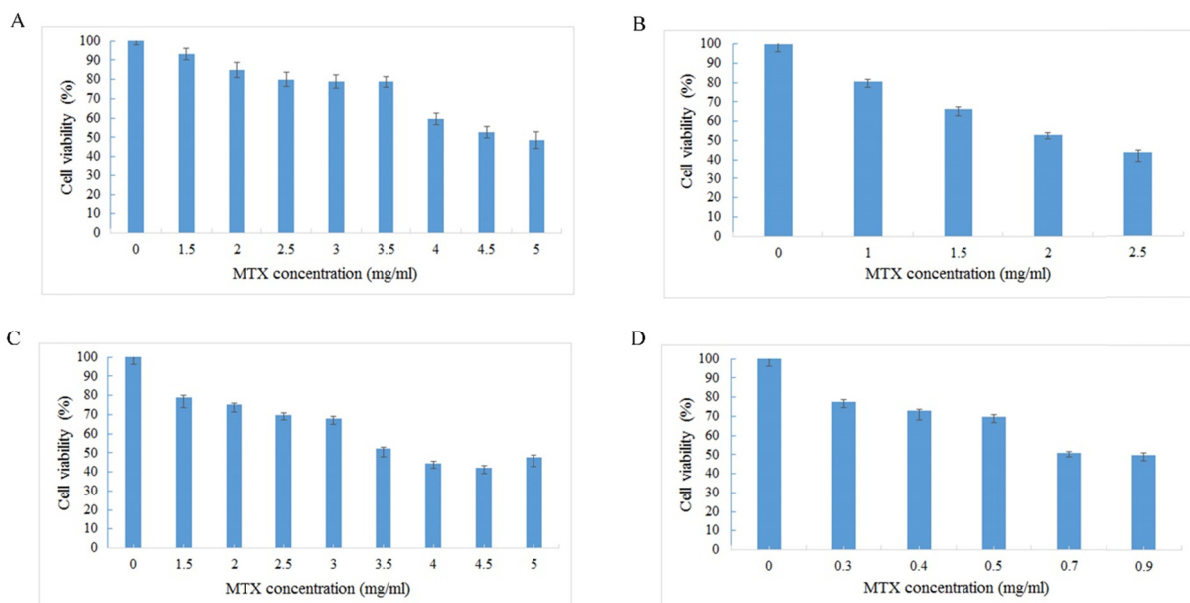

**Fig. 3.** In vitro cell viability of BT-474 cell line incubated with free MTX after 24 hours (A), liposomal MTX after 24 hours (B), free MTX after 48 hours (C) and liposomal MTX after 48 hours (D).

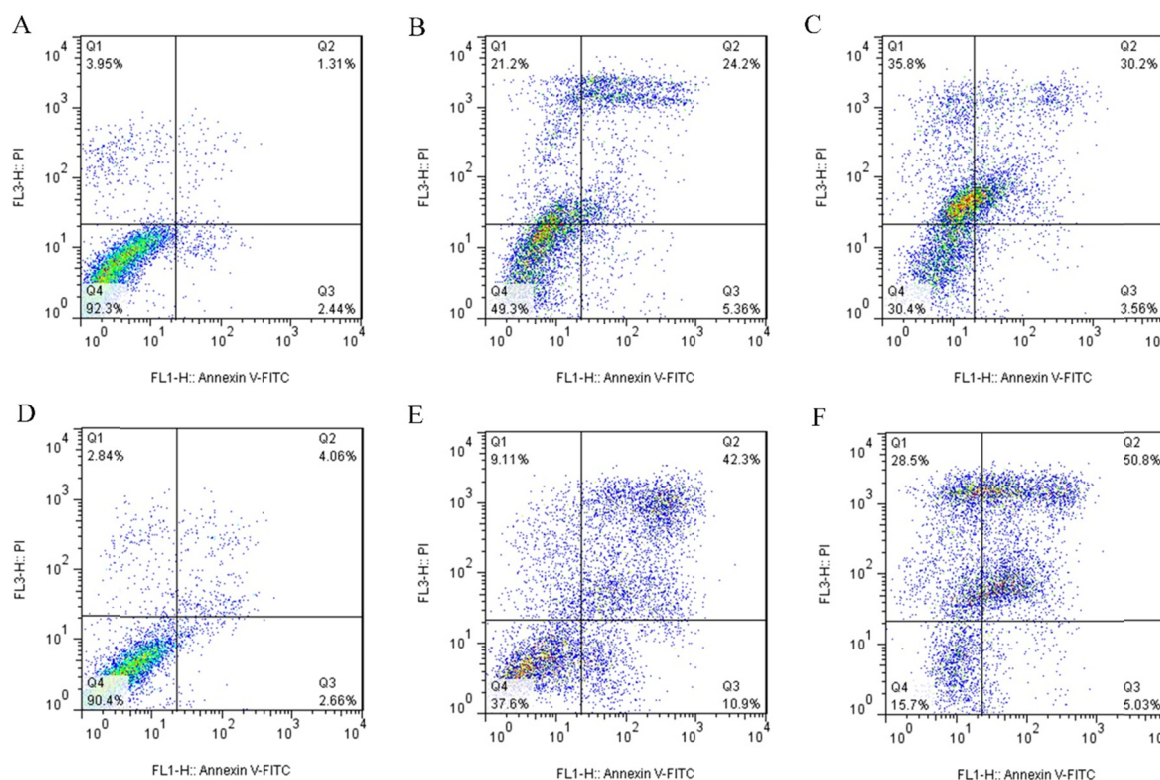


Fig. 4. Flow cytometry profiles of, controls after 24 hours (A), free MTX after 24 hours (B), liposomal MTX after 24 hours (C), controls after 48 hours (D), free MTX after 48 hours (E) and liposomal MTX after 48 hours (F).

24 and 48 hours, respectively. These results demonstrated that the amount of IC<sub>50</sub> in encapsulated form is less than the free drug form; also this value for 48 hours is <24 hours. Therefore, it should be mentioned that after 48 hours, the liposomal drug (MTX/Lip) has a greater cytotoxic effect on this cell line.

### Flow Cytometry

Flow cytometry was conducted to determine the cellular uptake efficacy of the nanoparticles. The BT-474 cells were incubated with free and liposomal MTX at 37° C for 24 and 48 hours. It should be noted that the early apoptosis of free and liposomal MTX after 24 hours was  $5 \pm 0.5\%$  and  $3.5 \pm 0.6\%$  and after 48 hours it was  $10 \pm 1\%$  and  $5 \pm 0.4\%$ . Furthermore, the late apoptosis of free MTX and liposomal MTX after 24 hours was  $24 \pm 1.1\%$  and  $30 \pm 1\%$  and after 48 hours it was  $(42 \pm 0.6\%$  and  $50 \pm 1\%)$ , respectively. As shown in Figure 4, the liposomal MTX could be successfully internalized by BT-474 breast cancer cell line. These results confirmed that MTX in liposomal form had a greater cytotoxic effect on these cells compared with free MTX. Furthermore, its cytotoxic effects were more significant after 48 hours than 24 hours.

### Discussion

Liposomes are a type of drug delivery system that improve the pharmacological properties of chemotherapeutic drugs by altering the biodistribution and pharmacokinetic properties of these drugs. The aforementioned nanoparti-

cles have specific properties that make them appropriate candidates for the drug delivery system. For example, liposomes cause slow and stable drug release, reduce the cytotoxicity of the drugs, and increase the accumulation of the drugs at the tumor site because of their special characteristics (31). Based on the aforementioned characteristics, in this study, liposomes were used as nanocarriers to treat breast cancer cells. In the present study, MTX was loaded into liposomal nanoparticles and its anti-cancer effect was evaluated in free (MTX) and liposomal (MTX/Lip) forms on BT-474 breast cancer cell line.

The mean hydrodynamic size of empty liposomes and MTX/Lip was 191.9 and 195 nm, respectively. The results of DLS showed that the addition of the MTX to liposomes did not have a significant effect on the size of the nanoparticles and this size was suitable to target breast cancer cells by passive targeting. Furthermore, the PDI of MTX/Lip nanoparticles was desirable and their surface charge was negative. This negative surface charge may prevent the accumulation of nanoparticles by creating electrostatic repulsion and also reduces adverse reactions between nanoparticles with plasma proteins and/or red blood cells (32).

Abdelbary et al determined the encapsulation efficiency (EE%) of MTX in nanostructured lipid carriers (NLCs), which was calculated above 60% (28). Ekinci et al calculated the drug loading content of chitosan nanoparticles loaded with methotrexate. One of the formulations had a drug loading content of 28 mg and EE% of 35%, and an-

other formulation had a drug loading content of 13 mg and EE% of 63% (33). In our study, the %EE was calculated to be about 98% which confirmed that the encapsulation efficiency of MTX in liposomes was desirable enough. Jin et al investigated the release of MTX from various micelle formulations in 2 different pH levels: physiological (pH = 7.4) and acidic (pH = 5). In one particular formulation and under similar conditions, the release of MTX from nanocarriers was only 20% at physiological pH (7.4) and approximately 60% at acidic pH (5) after 48 hours. Thus, the release of MTX was dependent on pH (34). In our study, the release of MTX from liposomal nanoparticles (MTX/ Lip) was investigated at 3 different pH levels: physiological (pH = 7.4), tumor surrounding (pH = 6.4), and endosomal environment (pH = 5.4) for 24 hours. At a particular time, the drug release increased with decreasing the pH. Thus, the drug release at physiological pH (pH = 7.4) was less than the other 2 pHs. It should be noted that the highest drug release rate was in acidic pH (pH = 5.4). As shown in Figure 2, after 24 hours, 90% of the drug was released at (PH = 5.4). As a result, it could be suggested that drug release in tumor surrounding environment is higher than healthy tissues, and this causes the maximum amount of drug to reach the cancer cells, and the healthy cells are less likely to be affected by the drug (Fig. 2).

Gorjikhah et al studied the cytotoxic effects of free and encapsulated MTX in polymer nanoparticles on the T47D breast cancer cell line at different concentrations. The IC<sub>50</sub> values of free MTX on T47D cells after 24, 48, and 72 hours were 0.391, 0.361, and 0.285 mg/mL, respectively. On the other hand, the IC<sub>50</sub> values of encapsulated MTX in polymer nanoparticles on T47D cells after 24, 48, and 72 hours were 0.318, 0.294, and 0.241 mg/mL, respectively. Thus, the cytotoxic effect of encapsulated MTX was greater than that of the free MTX (35). In this study, the cytotoxic effects of MTX and MTX/Lip at various concentrations (0.3-5 mg/mL) were investigated by the MTT assay on BT-474 breast cancer cell line. As shown in Figure 3, the IC<sub>50</sub> values of MTX after 24 and 48 hours were 4.85 and 3.62 mg/mL, respectively. Furthermore, the IC<sub>50</sub> values of MTX/Lip after 24 and 48 hours were 2.15 and 0.82 mg/mL, respectively. These results demonstrated that free MTX had lower cytotoxic effect on BT-474 breast cancer cell line than MTX/Lip, and for a particular drug form, cytotoxicity increased over time. These data confirmed that the differences in cytotoxicity for free and encapsulated MTX were significant.

In one study, Anne Marie Ciobanu et al created the liposomal MTX. The effect of MTX incorporated in liposomes was investigated in vitro on human lymphoblastic cell line K562. Their study showed that MTX incorporated into liposomes moderately reduced the proliferation of K562 cells, but significantly inhibited RNA synthesis (36).

Flow cytometry was used to confirm the uptake of free and liposomal MTX (MTX/Lip) by BT-474 breast cancer cells. The cytotoxic effect of these 2 forms increased over time. This Figure (Fig. 4) confirmed that the cytotoxicity effect of MTX/Lip was greater than MTX. Several studies demonstrated that the rate of apoptosis in liposomal MTX

was higher than free MTX, which was confirmed by our results (37-39).

### Conclusion

Nowadays, studies on nanoparticle formulations are ongoing. Moreover, liposome-based formulations have entered the clinical trials to treat a variety of cancers. Methotrexate is an anticancer drug that is commonly used to treat different cancers, including breast, lung, head and neck, et cetera. Because of special side effects of this chemotherapeutic drug, the liposomal MTX can be a promising choice for the treatment of breast cancer; however, more investigations are needed.

### Acknowledgment

The authors appreciate the Research Council of Qazvin University of Medical Sciences.

### Conflict of Interests

The authors declare that they have no competing interests.

*Ethical Approval:* IR.QUMS.REC.1397.175.

### References

1. Albeshan SM, Hossain SZ, Mackey MG, Brennan PC. Can Breast Self-examination and Clinical Breast Examination Along With Increasing Breast Awareness Facilitate Earlier Detection of Breast Cancer in Populations With Advanced Stages at Diagnosis? Clin Breast Cancer. 2020.
2. Hanikoglu A, Kucuksayan E, Hanikoglu F, Ozben T, Menounou G, Sansone A, et al. Effects of somatostatin, curcumin, and quercetin on the fatty acid profile of breast cancer cell membranes. Can J Physiol Pharmacol. 2020;98(3):131-8.
3. Nikkholi SK, Dorostkar R, Ranjbar S, Heydarzadeh H, Tat M, Ghalavand M, et al. Synergistic effect of expressed miR-128 and Puma protein on targeted induction of tumor cell apoptosis. Iran J Biotechnol. 2016;14(3):185.
4. Waks AG, Winer EP. Breast Cancer Treatment: A Review. JAMA. 2019;321(3):288-300.
5. Farasat A, Rahbarizadeh F, Ahmadvand D, Yazdian F. Optimization of an anti-HER2 nanobody expression using the Taguchi method. Prep Biochem Biotechnol. 2017;47(8):795-803.
6. Nikkholi SK, Rahbarizadeh F, Ranjbar S, Khaleghi S, Farasat A. Liposomal nanoparticle armed with bivalent bispecific single-domain antibodies, novel weapon in HER2 positive cancerous cell lines targeting. Mol Immunol. 2018;96:98-109.
7. Akram M, Iqbal M, Daniyal M, Khan AU. Awareness and current knowledge of breast cancer. Biol Res. 2017;50(1):33.
8. Lee JJ, Saiful Yazan L, Che Abdullah CA. A review on current nanomaterials and their drug conjugate for targeted breast cancer treatment. Int J Nanomedicine. 2017;12:2373-84.
9. Alavi AS, Meshkini A. Fabrication of poly(ethylene glycol)-coated mesoporous nanocomposite ZnO@Fe<sub>2</sub>O<sub>3</sub> for methotrexate delivery: An integrated nanopatform for dual-mode cancer therapy. Eur J Pharm Sci. 2018;115:144-57.
10. Vaidya FU, Sufiyah Chhipa A, Mishra V, Gupta VK, Rawat SG, Kumar A, et al. Molecular and cellular paradigms of multidrug resistance in cancer. Cancer Rep. 2020:e1291.
11. Bohme D, Kriehoff J, Beck-Sickingher AG. Double Methotrexate-Modified Neuropeptide Y Analogues Express Increased Toxicity and Overcome Drug Resistance in Breast Cancer Cells. J Med Chem. 2016;59(7):3409-17.
12. Gu G, Dustin D, Fuqua SA. Targeted therapy for breast cancer and molecular mechanisms of resistance to treatment. Curr Opin Pharmacol. 2016;31:97-103.
13. Nunez C, Capelo JL, Igrejas G, Alfonso A, Botana LM, Lodeiro C. An overview of the effective combination therapies for the treatment

- of breast cancer. *Biomaterials*. 2016;97:34-50.
14. Uddin N, Ahmed S, Khan AM, Mazharol Hoque M, Halim MA. Halogenated derivatives of methotrexate as human dihydrofolate reductase inhibitors in cancer chemotherapy. *J Biomol Struct Dyn*. 2020;38(3):901-17.
  15. Yu CP, Hsieh YC, Shia CS, Hsu PW, Chen JY, Hou YC, et al. Increased Systemic Exposure of Methotrexate by a Polyphenol-Rich Herb via Modulation on Efflux Transporters Multidrug Resistance-Associated Protein 2 and Breast Cancer Resistance Protein. *J Pharm Sci*. 2016;105(1):343-9.
  16. Ferreira M, Chaves LL, Lima SA, Reis S. Optimization of nanostructured lipid carriers loaded with methotrexate: A tool for inflammatory and cancer therapy. *Int J Pharm*. 2015;492(1-2):65-72.
  17. Hess JA, Khasawneh MK. Cancer metabolism and oxidative stress: Insights into carcinogenesis and chemotherapy via the non-dihydrofolate reductase effects of methotrexate. *BBA Clin*. 2015;3:152-61.
  18. Xu D, Lu ST, Li YS, Baidya A, Mei H, He Y, et al. Evaluation of methotrexate-conjugated gadolinium(III) for cancer diagnosis and treatment. *Drug Des Devel Ther*. 2018;12:3301-9.
  19. Shah VV, Lin EJ, Reddy SP, Wu JJ. Methotrexate. Therapy for Severe Psoriasis: Elsevier; 2016. p. 37-48.
  20. Wu CW, Liu HC, Yu YL, Hung YT, Wei CW, Yiang GT. Combined treatment with vitamin C and methotrexate inhibits triple-negative breast cancer cell growth by increasing H<sub>2</sub>O<sub>2</sub> accumulation and activating caspase-3 and p38 pathways. *Oncol Rep*. 2017;37(4):2177-84.
  21. Wu D, Si M, Xue HY, Wong HL. Nanomedicine applications in the treatment of breast cancer: current state of the art. *Int J Nanomedicine*. 2017;12:5879-92.
  22. de Oliveira CP, Bottenbender SL, Prado WA, Beckenkamp A, Asbahr AC, Buffon A, et al. Enhanced and Selective Antiproliferative Activity of Methotrexate-Functionalized-Nanocapsules to Human Breast Cancer Cells (MCF-7). *Nanomaterials (Basel)*. 2018;8(1).
  23. Riaz MK, Riaz MA, Zhang X, Lin C, Wong KH, Chen X, et al. Surface Functionalization and Targeting Strategies of Liposomes in Solid Tumor Therapy: A Review. *Int J Mol Sci*. 2018;19(1).
  24. Sercombe L, Veerati T, Moheimani F, Wu SY, Sood AK, Hua S. Advances and Challenges of Liposome Assisted Drug Delivery. *Front Pharmacol*. 2015;6:286.
  25. Dennis MJ. The impact of COVID-19 on the world economy and higher education. *Enroll. Manag. Rep*. 2020;24(9):3-.
  26. Babaie S, Ghanbarzadeh S, Davaran S, Kouhsoltani M, Hamishehkar H. Nanoethosomes for dermal delivery of lidocaine. *Adv Pharm Bull*. 2015;5(4):549.
  27. Jouyban A, Shaghghi M, Manzoori JL, Soleymani J, JaliVaez-Gharamaleki J. Determination of methotrexate in biological fluids and a parenteral injection using terbium-sensitized method. *Iran J Pharm Res*. 2011;10(4):695.
  28. Abdelbary G, Haider M. In vitro characterization and growth inhibition effect of nanostructured lipid carriers for controlled delivery of methotrexate. *Pharm Dev Technol*. 2013;18(5):1159-68.
  29. Sabeti B, Noordin MI, Mohd S, Hashim R, Dahlan A, Akbari Javar H. Development and characterization of liposomal doxorubicin hydrochloride with palm oil. *Biomed Res Int*. 2014;2014.
  30. Mosmann T. Rapid colorimetric assay for cellular growth and survival: application to proliferation and cytotoxicity assays. *J Immunol Methods*. 1983;65(1-2):55-63.
  31. Sharma A, Jain N, Sareen R. Nanocarriers for diagnosis and targeting of breast cancer. *Biomed Res Int*. 2013;2013.
  32. Suk JS, Xu Q, Kim N, Hanes J, Ensign LM. PEGylation as a strategy for improving nanoparticle-based drug and gene delivery. *Adv Drug Deliv Rev*. 2016;99:28-51.
  33. Ekinci M, Ilem-Ozdemir D, Gundogdu E, Asikoglu M. Methotrexate loaded chitosan nanoparticles: Preparation, radiolabeling and in vitro evaluation for breast cancer diagnosis. *J Drug Deliv Sci Technol*. 2015;30:107-13.
  34. Xie J, Fan Z, Li Y, Zhang Y, Yu F, Su G, et al. Design of pH-sensitive methotrexate prodrug-targeted curcumin nanoparticles for efficient dual-drug delivery and combination cancer therapy. *Int J Nanomed*. 2018;13:1381-98.
  35. Gorjikhah F, Azizi Jalalian F, Salehi R, Panahi Y, Hasanzadeh A, Alizadeh E, et al. Preparation and characterization of PLGA-beta-CD polymeric nanoparticles containing methotrexate and evaluation of their effects on T47D cell line. *Artif Cells Nanomed Biotechnol*. 2017;45(3):432-40.
  36. Ciobanu AM, Bărcă M, Manda G, Dragomiroiu G, Baconi DL. Methotrexate liposomes-a reliable therapeutic option. *Liposomes*. 2017:267.
  37. Lo YL, Lee HP, Tu WC. The use of a liposomal formulation incorporating an antimicrobial peptide from tilapia as a new adjuvant to epirubicin in human squamous cell carcinoma and pluripotent testicular embryonic carcinoma cells. *Int J Mol Sci*. 2015;16(9):22711-34.
  38. Koshkaryev A, Piroyan A, Torchilin VP. Increased apoptosis in cancer cells in vitro and in vivo by ceramides in transferrin-modified liposomes. *Cancer Biol Ther*. 2012;13(1):50-60.
  39. Kalantar M, Rezaei M, Moghimipour E, Bavarsad N, Kalantari H, Varnaseri G, et al. Evaluation of Apoptosis Induced by Celecoxib Loaded Liposomes in Isolated Rat Hepatocytes. *Jundishapur J Nat Pharm Prod*. 2015;10(3).